



**HAL**  
open science

## Neutron Displacement Damage Cross Section in GaN: Numerical Evaluations and Differences With Si

Damien Lambert, Julien Parize, Nicolas Richard, Mélanie Raine, Olivier Duhamel, Claude Marcandella, Arthur Losquin, Anne Hémercyck, Christophe Inguibert, Philippe Paillet

► **To cite this version:**

Damien Lambert, Julien Parize, Nicolas Richard, Mélanie Raine, Olivier Duhamel, et al.. Neutron Displacement Damage Cross Section in GaN: Numerical Evaluations and Differences With Si. IEEE Transactions on Nuclear Science, 2023, 70 (8), pp.1870 - 1877. 10.1109/TNS.2023.3265463 . hal-04074966

**HAL Id: hal-04074966**

**<https://laas.hal.science/hal-04074966v1>**

Submitted on 19 Apr 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Neutron displacement damage cross-section in GaN: numerical evaluations and differences with Si

Damien Lambert, *Senior Member, IEEE*, Julien Parize, Nicolas Richard, Mélanie Raine, *Member, IEEE*, Olivier Duhamel, Claude Marcandella, Arthur Losquin, Anne Hemeryck, Christophe Inguibert, and Philippe Paillet, *Fellow, IEEE*,

**Abstract**—The displacement damage cross-section of the neutron - GaN interaction is calculated in the energy range from meV to GeV. Different calculation methods are used and discussed to estimate the modeling uncertainty. The Non-ionizing energy loss (NIEL) and the relative damage factors are also deduced. Differences with the neutron - Silicon interactions are presented and the impacts on the estimation of Total Non-Ionizing Dose (TNID) levels are evaluated as a function of neutron energy.

**Index Terms**—Displacement Damage, neutron, GaN, NIEL, TNID, cross-section, Geant4, Monte Carlo

## I. INTRODUCTION

IRRADIATIONS can induce two types of cumulative effects in electronics via ionizing and non-ionizing mechanisms. While total ionizing dose effects (TID) mainly degrade dielectrics, non-ionizing dose effects (TNID), so-called displacement damage dose (DDD) effects, are mainly induced in the semiconductor constituting the conduction channel of electronic carriers. DDD effects in microelectronics have been studied extensively for a long time [1][2][3]. They result from the creation of defects within semiconductors and can be induced by different types of particles such as heavy ions, protons, neutrons or electrons. The panel of produced defect types can be very different depending on the incident particle, its energy and the target material compounds. The most studied material is naturally silicon, another one being GaAs [4][5][6].

Some GaN devices show the potential to be extremely radiation-tolerant for dose radiation in space [7]. GaN components seem to have good Single Event Effect predispositions for operation under space radiation environment [8][9], but less under terrestrial neutrons [10]. It is thus necessary to assess specific dose effects induced by neutrons in this material [11]-[16]. Usually [17], in order to limit the number of experimental TNID characterizations for the qualification of electronics in a radiation environment, the measured degradations are reduced to a single type of particle, at a given energy and a given fluence. This is done using an "equivalent damage factor" that we will call F. These so-called F factors are based on displacement damage cross-section ("D") ratios. For silicon components, it is usual to use a Si neutron equivalence at 1 MeV in a neutron environment [18][19] and a Si proton equivalence at 10 MeV in a proton environment [8].

Today, there are only a few studies to know about neutron NIEL in GaN and no reference standard validated by a standards organization like in Si and GaAs. Until very recently, to our knowledge, there were no available data of displacement damage cross-sections induced by neutrons in GaN components. This study aims at providing the community with displacement damage cross section, NIEL and relative damage factor of the neutron-GaN interaction from low to high energy with different calculation methods to estimate a modeling uncertainty. Since a few months (July 2022), the SR-NIEL team [3] proposed model-based calculations for the NIEL of n-GaN interactions at energies below 20 MeV. In this study, these new data are used as a reference for comparison.

Experimenters use NIEL curves of different materials and particles in order to test the effects of damage displacement on different available irradiation machines. This is to validate or invalidate equivalence between particle effects [20]. Without any data consistent with GaN device technology, experimenters may, by mistake, by habit or for lack of anything better, use the widely used Silicon data [21][22]. It would not be very relevant according to the fact that neutron nuclear interaction cross sections can exhibit large differences from one material to another. The main goal of this study is to perform an initial characterization of displacement damage cross sections in GaN along with their sensitivity to model variations, as compared against corresponding Si data. The secondary objective is to determine some of the energy characteristics of primary knock-on atoms (PKA) from n-GaN interactions. The definition of the PKA characteristics being the first step of a more complete displacement damage defect study, the data provided here will be used in future work, following the scientific approach described in [23].

## II. DISPLACEMENT DAMAGE CROSS-SECTION: A TWO STEP PROCESS

As done in previous studies [4][5][24], the displacement damage cross-section is calculated with the following formula:

$$D(E_n) = \sum_R \int_0^\infty E_r \cdot n(R, E_r) \cdot \frac{d\sigma_R(E_n, E_r)}{dE_r} dE_r \quad (1)$$

Damien Lambert, Mélanie Raine, Olivier Duhamel, Claude Marcandella, Arthur Losquin and Philippe Paillet are with CEA, DAM, DIF, F-91297 Arpajon, France (e-mail: damien.lambert@cea.fr)

Julien Parize is with CEA, DAM, DIF, F-91297 Arpajon, France and LAAS-CNRS, Université de Toulouse, CNRS, Toulouse, France

Nicolas Richard is with CEA, DAM, DIF, F-91297 Arpajon, France and University of Paris-Saclay, CEA, Laboratoire Matière en Conditions Extrêmes, F-91680 Bruyères-le-Châtel, France

Anne Hemeryck is with LAAS-CNRS, Université de Toulouse, CNRS, Toulouse, France

Christophe Inguibert is with ONERA, Toulouse, France.

where:

- $D$  is the displacement damage cross section expressed in [MeV.mb]. This term is also called microscopic displacement kerma.
- $E_n$  is the incident neutron energy
- $R$  the secondary particle type: PKA type
- $E_r$  is the energy of the recoil particle expressed in [MeV]
- $n(R, E_r)$  is the energy partition function of the Recoil particle as a function of the  $E_r$  energy which can be calculated by different formula and numerical methods exist to evaluate it as discussed further,
- $\sigma_R(E_n, E_r)$  is the production cross section of the R recoil particle expressed in [mb]

The two main parameters are:

- the production cross-sections, which can be estimated with the study of secondary particles from the neutron-atom interaction; and
- either, the energy partition function, which defines the part of the energy which will be transferred into displacement damage, or equivalently the displacement energy, which is the product of the energy partition function with the PKA energy:

$$E_{displacement} = E_r \times n(R, E_r) \quad (2)$$

Fig. 1 shows a comparison between the displacement damage cross-section  $D$  of neutrons in silicon calculated using Geant4 with data from the literature. As can be seen, our calculations are in good agreement with the literature. ASTM722-19 is based on the NJOY tool, which uses the B-VII version of the evaluated nuclear data files (ENDF) database. Geant4 uses another ENDF database version (the ENDF/B-VIII.0 for Geant4-10-05). The small differences come from the different database versions and energy partition functions. Details of our calculations are given in the two following sub-sections.

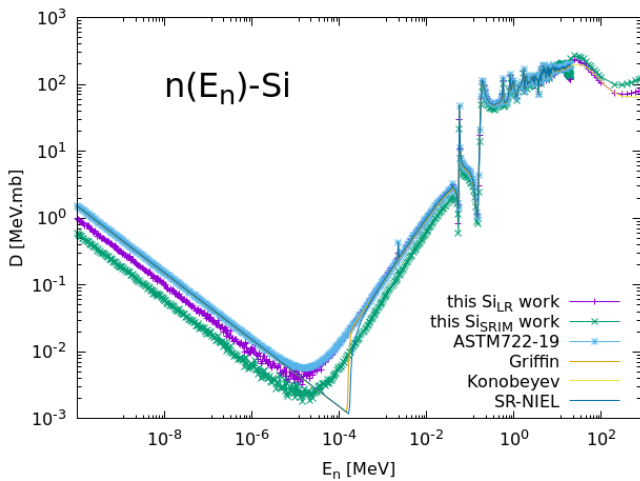


Fig. 1. Displacement damage cross-section in silicon material: SR-NIEL [5], ASTM722-19 norm [4], Griffin work [24], Konobeyev work [24], and this silicon work with two options (LR and SRIM).

### A. Neutron interaction with the target atoms

The estimation of the damage cross-sections can be carried

out in either of two ways: a) by using Monte Carlo tools (such as MCNP or Geant4) which use the nuclear data files to generate recoil particles that are then followed via charged particle transport modeling to yield the damage assessment; or b) by using processing codes (such as NJOY, FRENDY, or GRUCON) which use the characteristics from the nuclear data files in conjunction with kinematic constraints and apply damage partition functions to the recoil particle energy spectra. In this work, Geant4 has been used [25][26][27]. The energy spectrum from 0.1 meV to 1 GeV has been split into a large number (~700) of smaller energy bins (a few percent of mean neutron energy as done in [4]) in order to take the neutron resonances into account. The dimensions of the target volume are large (greater than 1 m) in order to record all cascades of events. Each simulation takes into account a large number of interaction histories to have a good statistical response (~10<sup>5</sup>). The Geant4 master version (10.5) with capture, fission, elastic (high precision) and Bertini (high precision) INC (intranuclear cascade) models has been used. The results are stored into a database with one file for each energy.

### B. The energy partition function

The energy partition function is the second key parameter to estimate the displacement cross-section. Different formulas and methods exist to calculate it, and we have chosen to focus on four methods.

The first one is based on the Robinson (“LR”) formula [28] based on [29][30]. This formula (3) depends on the atomic number  $Z$  and mass number  $A$  of the target material ( $Z_L$  and  $A_L$ ) and of the PKA ( $Z_R$  and  $A_R$ ). As presented by Jun [31] and Fig. 1, this formula gives good results for silicon  $D$  calculations.

$$LR(E_r) = \frac{1}{1 + F_L(3.4008\varepsilon^{1/6} + 0.40244\varepsilon^{3/4} + \varepsilon)} \quad (3)$$

where:

$$\begin{aligned} E_r &\text{ is the recoil energy} \\ \varepsilon &= \frac{E_r}{E_L} \\ E_L &= 30.724 Z_R Z_L \sqrt{Z_R^{2/3} + Z_L^{2/3}} \frac{A_R + A_L}{A_L} \\ F_L &= \frac{0.0793 Z_R^{2/3} Z_L^{1/2} (A_R + A_L)^{3/2}}{(Z_R^{2/3} + Z_L^{2/3})^{3/4} A_R^{3/2} A_L^{1/2}} \end{aligned}$$

The Lindhard model is limited to ion energies less than about ( $24.8 \times Z^{4/3} \times A$  [keV]), which means ~4.6 MeV for N and ~170 MeV for Ga. As noticed in [28], this formula applies only to monatomic systems.

The second formula type, that we call “LT<sub>Ed</sub>”, is the previous Robinson formula, but with the additional application of the Kinchin-Pease [32] treatment of the threshold for lattice displacement using a displacement threshold energy ( $E_d$ ), as used in [3] and [4]:

$$LT_{Ed}(E_r) = \begin{cases} 0, & \text{if } E_r < E_d \\ \frac{2}{3} \left( \frac{E_r - E_d}{E_d} \right) LR(E_r), & \text{if } E_d \leq E_r < \frac{2E_d}{0.8} \\ LR(E_r), & \text{if } E_r \geq \frac{2E_d}{0.8} \end{cases} \quad (4)$$

This formula is almost the same as the one described in [33]. In our case, between  $E_d$  and  $(2E_d)/0.8$ , we neglect the energy transmitted to the electrons. As illustrated in the following figures, for this study, this approximation has little significant influence on the results. It gives good results for silicon even if improvements are still in progress for electron irradiations [34].

The third method is based on the SRIM database [36]. The displacement energy is estimated by integrating the nuclear stopping power for each ion ( $Z$ ) type in a target (Si or GaN for this study). This method uses a Binary Collision Approximation (BCA).

The fourth method is based on the TRIM (Transport of ions in matter) program included in the SRIM software [36]. This Monte Carlo tool allows obtaining precise data on the course of the collisions cascades. Thus, with a significant number of Monte Carlo events, it is possible to obtain the average percentage of recoil energy. We have therefore performed simulations of ions from  $Z=1$  to  $Z=32$  at energies from a few eV to 100 MeV (1 GeV for some ions according to the energy of the secondary particles of n-GaN). The layer thickness of gallium nitride is adapted to the PKA range. We have observed a stabilization of the data around 4000 simulations leading to accurate results. Thus, 4000 ion-runs have been performed for each ion type and each energy level. The calculation method "Detailed Calculation with full Damage Cascades" has been used. This method is slower than the calculation method "Ion Distribution and Quick Calculation of Damage" (which gives the SRIM database results) but takes into account every collision of the recoil particle until the energy drops below the lower energy thresholds [37]. For the energy partitioning, the two methods give the same result and for the defect number estimation, it has been demonstrated that the full cascade option is less accurate than the quick calculation [38].

### III. DATABASE VERIFICATION OF THE NEUTRON-NITROGEN (N-N) AND NEUTRON-GA (N-GA) INTERACTION MODELING

The first step is to do a verification of the results of our interaction database by comparison with the literature. Fig. 2 and Fig. 3 present a comparison between the interaction cross-sections (elastic, inelastic, capture and total) of n-N and n-Ga with the ENDFB-VIII.0 database from JANIS [43]. The results are very close because the Geant4 modeling uses the same underlying ENDF/B-VII nuclear data file to describe the reaction probabilities. Other databases available on JANIS have been used for comparison but they are not displayed in order to leave a readable figure.

For n-N interactions, the Geant4-produced cross sections for natural N are in good agreement with those displayed in the JANIS data viewer. For the n-Ga interaction, the calculated data of natural Ga are a data mix of the two isotope interactions:  $n\text{-}^{69}\text{Ga}$  (60.1%) and  $n\text{-}^{71}\text{Ga}$  (39.9%). Thus, we consider that the calculated and the JANIS data cross-sections are in good

agreement within the uncertainty from the different isotope mixes. The elastic interaction is the main contributor to the total cross-section for n-N interactions.

For n-Ga interactions, it is more complex: the cross-section is mainly driven by:

- capture at low energies ( $< \sim 10$  meV),
- elastic interaction, at medium energies
- inelastic reaction at high energies ( $>$  a few MeV).

Only a few data are available in the literature for energies above 100 MeV. Thus, the verification by comparison is not accurate in the 100 MeV – 1 GeV energy range.

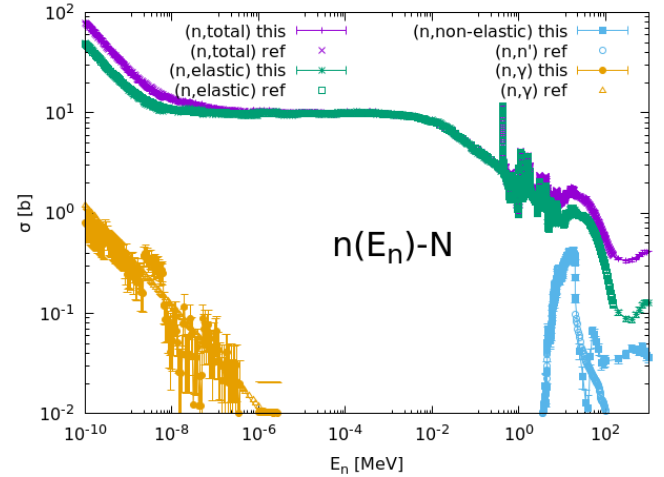


Fig. 2. Neutron – Nitrogen cross-sections: “ref” is from ENDF/B-VIII.0 data [43] and “this” is from this work.

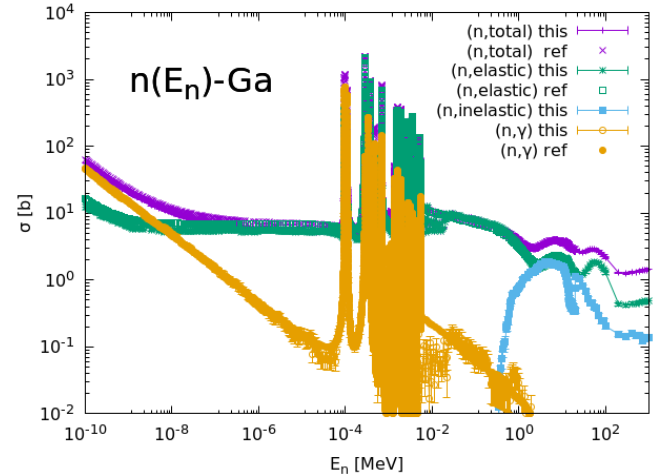


Fig. 3. Neutron – Gallium cross-sections: “ref” is from ENDF/B-VIII.0 data [43] and “this” is from this work.

## IV. N-GAN RESULTS

### A. Contributions to the cross-section

Fig. 4 presents the n-GaN cross-sections as a function of neutron energy. The n-GaN cross-sections are the average of the n-Ga and n-N ones, so it is a mix of the n-N and n-Ga interactions:

- the main contributors are:
  - the elastic reaction (such as n-N) below  $\sim 20$  MeV

- and the inelastic reaction at high energy,
- the order of magnitude of the cross-section is close to the n-Ga one.

The resonance phenomena are smoothed by the sum or conjoint contribution of both interactions. The amplitudes of the n-Ga resonances are smaller, and those of the n-N have almost disappeared.

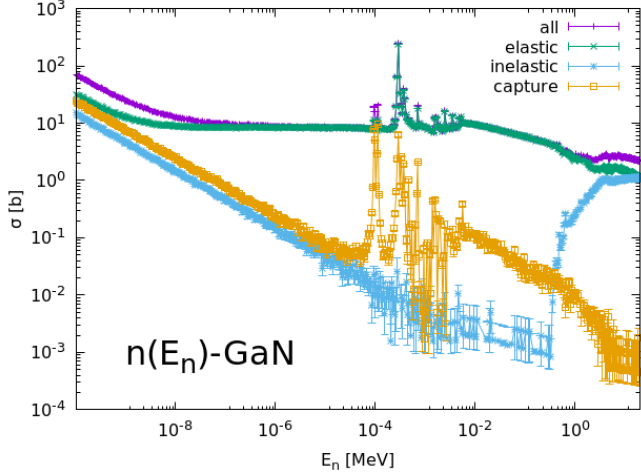


Fig. 4. Neutron – GaN cross-sections: this work.

### B. Energy partition functions in GaN

Fig. 5 and Fig. 6 show the partition damage energy as a function of the primary recoil energy of the two main PKAs: N and Ga. The displacement energy is the product of this distribution function with the PKA energy ( $E_r$ ). The displacement threshold energy to use for GaN is not exactly defined. According to [39], the minimal energies of defect formation is 18 eV for Ga and 22 eV for nitrogen. [40] used a displacement energy of 21.8 eV for N in GaN obtained from an experiment [41] and a displacement energy of 22.0 eV for Ga in GaN which is a result of theoretical calculation [42]. SR-NIEL [5] proposes 21 eV for N and 21.5 eV for Ga. We choose to take  $\sim 20$  eV as a medium value and +50% for exploration. The LT(GaN/2) curves are close to each other for this difference in threshold displacement energy and these curves are similar to the corresponding TRIM results (cf. Fig. 5 and Fig. 6).

We investigated six methods to determine the energy partition functions:

- LR(K): where the Robinson function uses the average Z and A of the two target atoms, i.e., the “GaN/2” K atom.
- LR(GaN/2) is the average of the Robinson function of N and the Robinson function of Ga.
- LT(GaN/2  $E_d = 20$  eV): is the average of the Robinson function of N and the Robinson function of Ga, with a low displacement energy threshold of 20 eV. This threshold value is just below the SR-NIEL one.
- LT(GaN/2  $E_d = 30$  eV): is the average of the Lindhard-Robinson function of N and the Lindhard-Robinson function of Ga, with a high displacement energy threshold of 30 eV. This threshold value is +50% above the previous value.

- SRIM: where nuclear stopping power from the SRIM database is used.
- TRIM: where the Monte Carlo results are used with the default displacement energy thresholds (25 and 28 eV).

We should mention that the Robinson method used for four energy partition functions is validated only for monatomic systems, which is not the case of GaN. But as can be seen between 100 eV and 1 MeV, all of the six results are close. At low energy, the oscillations of SRIM are caused by the limit of the number of significant digits on the output. Near the displacement threshold ( $\sim 20$  eV), the formulas differ slightly, depending on whether or not they take into account the threshold energy. As it was studied in [44], the damage energy functions of a polyatomic material are not a combination of those of the elements of this material. Indeed, depending on the nature of the PKA, one of the atoms of the target material will be privileged during the displacements. Thus, we believe that the presented approach should be complemented by molecular dynamics simulations in order to estimate the uncertainty of the functions.

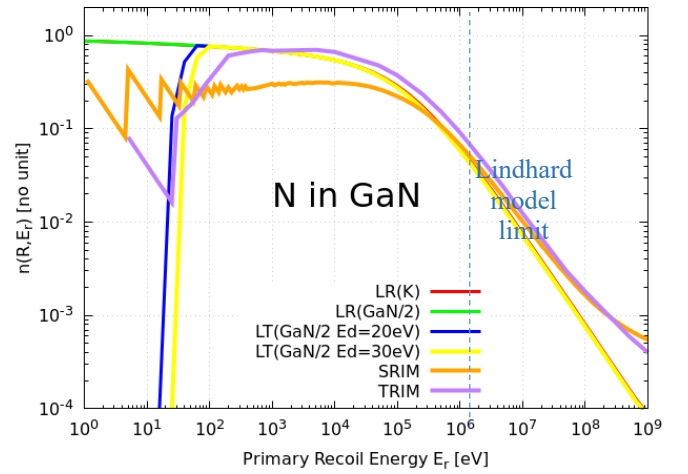


Fig. 5. Partition function of displacement damage energy as a function of primary recoil energy of N in GaN for the six energy partition functions.

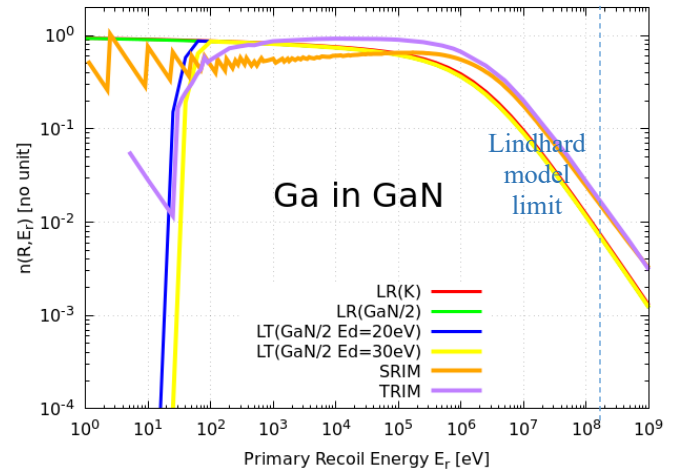


Fig. 6. Partition function of displacement damage energy as a function of primary recoil energy of Ga in GaN for the six energy partition functions.



Above 10 MeV, TRIM results are slightly above those from analytical models for this energy range. For the intermediate range of neutron-induced PKA energies, the results are close. With SRIM and TRIM, at high energy (above Lindhard model limit) the N ion shows an increase in the displacement deposit. That increase is not observed for the Ga ion, which is heavier and has a higher Lindhard model limit.

### C. Displacement damage cross-section and NIEL

Fig. 7 presents the results of the Displacement damage cross-section in Si and GaN based on the production cross sections estimated with Geant4 and the six energy partition functions calculated following the different methods. Our calculations are compared to the new SR-NIEL GaN data.

As can be seen, the LR and LT assumptions have little influence on the result. Although the two LR formulas used are not identical, the obtained results are close ( $<1\%$ ) as for the LT and LR values. The threshold value has little influence on the results. The results for the SRIM function are slightly different: below for energies below MeV and above for energies above. The differences can go up to a ratio of 2. The results for the TRIM function are slightly different: they are below for energies under MeV and above otherwise. At low energies, one would think that the different threshold energy assumptions would induce differences, but the  $^{14}\text{N}(n,p)^{14}\text{C}$  reaction predominates the other reactions on the lower energy range. The importance of the large neutron cross section from the  $\text{N14}(n,p)$  reaction was recently reflected in observed Single Event Effects in SRAMs [45] and is seen again in this analysis.

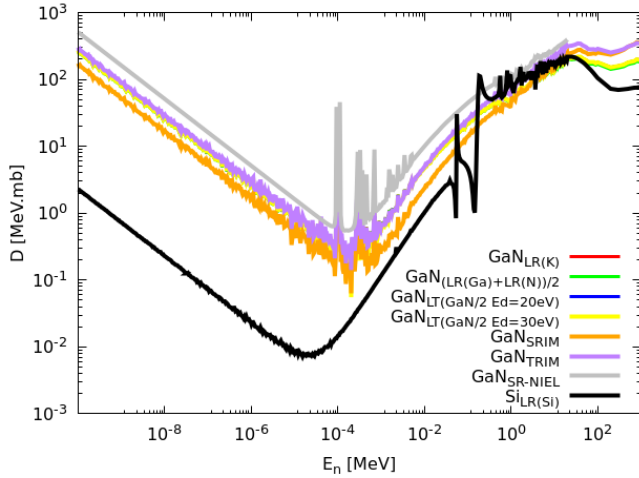


Fig. 7. Neutron Displacement damage cross-sections in Si and GaN.

When comparing the cross sections of the two materials, it can be noticed that:

- at low and high energies: D is larger for GaN than for Si;
- at energies close to MeV: D is slightly higher for Si than for GaN;
- there are more resonances for Si.

One can convert displacement damage cross sections to NIEL with the following equation:

$$\text{NIEL}[\text{MeV.cm}^2/\text{g}] = D[\text{MeV.mb}] \times \frac{N_A[\text{mol}]}{M[\text{g/mol}]} \times 10^{-27} \quad (5)$$

Thus, for silicon with  $M = 28.086 \text{ g/mol}$  the relation between D and NIEL is:  $1 \text{ MeV.mb} = 2.144 \times 10^{-5} \text{ MeV.cm}^2/\text{g}$ . For GaN with  $M = 83.73 \text{ g/mol}$ , the relation between D and NIEL is:  $1 \text{ MeV.mb} = 7.19 \times 10^{-6} \text{ MeV.cm}^2/\text{g}$ .

By converting the displacement damage cross sections to NIEL (Fig. 8), the order of the curves changes. In contrast to the displacement damage cross section where silicon has the smallest values, the NIEL values of Si are larger than that of GaN between  $\sim 0.1 \text{ MeV}$  and  $\sim 10 \text{ MeV}$ .

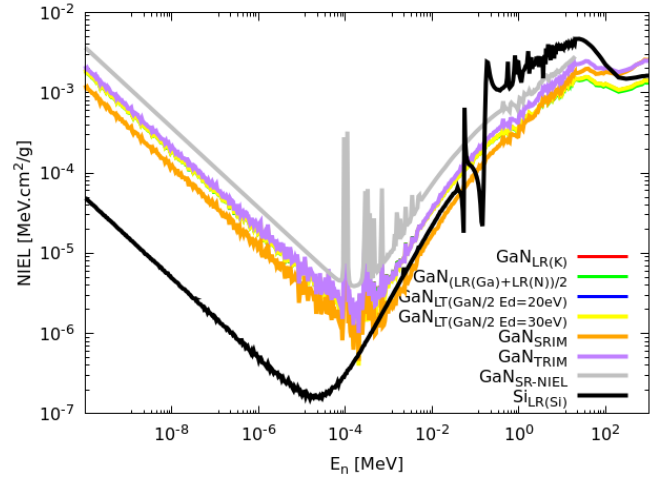


Fig. 8. NIEL data calculated in Si and GaN.

### D. Relative damage factors

The relative damage factor is a parameter used to estimate the 1 MeV equivalent fluence of a given neutron spectrum [19]. It is calculated from the NIEL curves or displacement damage cross section curves, which are normalized to 1.0 for an energy of 1 MeV. This factor makes it possible to carry out comparisons between experimental irradiations of electronic devices at fission-based neutron facilities where the effective neutron damage energy is above 0.1 MeV and where the dosimetry for displacement damage is expressed in 1 MeV equivalent neutron fluence in Si or GaN.

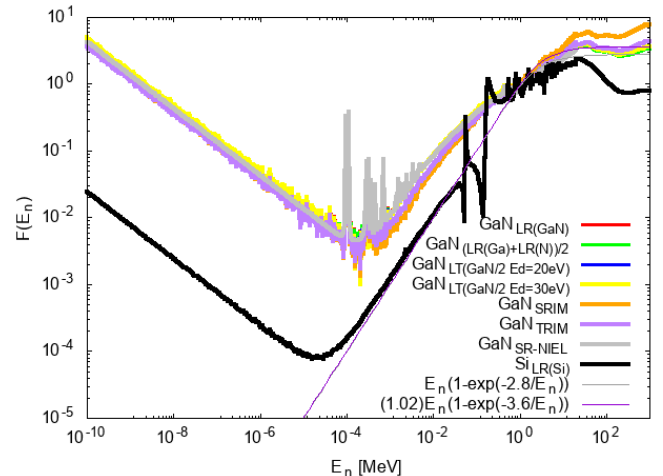


Fig. 9. Relative damage factor  $F(E_n)$  in GaN, Si and [2][3] Si formula.

Fig. 9, showing this relative damage factor in GaN and Si, clearly illustrates that the GaN function is larger than the Si function. The differences can be up to an order of magnitude. The remarks are identical for the historical exponential ( $a \cdot E_n (1 - \exp(-A/E_n))$  [1][2]) formula for silicon. By fitting Smits experimental data, Messenger obtained  $a=1.02$  and  $A=3.6$  MeV [2]. With other experimental data, [3] obtained different values:  $a=1.0$  and  $A=2.8$  MeV. These formulas smooth the resonance values.

In order to not underestimate the TNID level, it is then essential not to use the Silicon equivalence function for GaN components.

### E. PKA contributions to the displacement damage

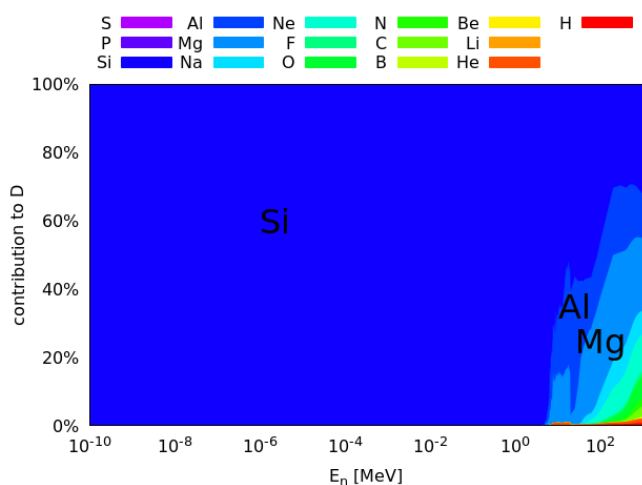


Fig. 10. PKA contributions to the n-Si displacement damage cross-section (with  $LTE_d$  (21 eV) energy partition function).

Fig. 10 and Fig. 11 illustrate the contributions of the different PKA species to the displacement cross-section for Si and GaN respectively.

For silicon, the silicon PKA is the first contributor for energies below a few tens of MeV. Mg and Al ions are also important contributors for energies above  $\sim 10$  MeV. Above 100 MeV, the contributions of Na, Ne, F and O ions increase with increasing neutron energy. At energies close to 1 GeV, almost all ions with an atomic number lower than silicon participate in the displacement effects.

For GaN, the distribution is different depending on the energy range:

- below 10 eV, the C ion is the first contributor and H the second. These ions come from the  $n + {}^{14}\text{N} \rightarrow p + {}^{14}\text{C}$  reaction;
- between  $\sim 1$  and 100 keV, the N ion is the first contributor (more than 70% weight) and Ga is the second;
- around 1 MeV, the contributions of N and Ga ions are almost equal;
- around 10 MeV, the Ga ion is the first contributor at more than 70% and the N the second; and
- near 1 GeV, the heavy ions (Ga, Zn, Cu, Ni, Co, Fe, Mn, Cr, V, Ti, Sc, Ca, K, etc.) share the main

contribution while the lightest ions ( $Z < 7$ ) have only a small contribution.

The distributions of PKA types are very different between n-Si and n-GaN. For silicon, the Si PKA is the first contributor over a large part of the energy range. For GaN, we have to look at different types of PKA with different masses. Indeed, N and C are lighter than Ga and Zn. As seen in SiGe [47], it is likely that light and heavy PKAs have different responses. This will be investigated with further modelling such as molecular dynamics.

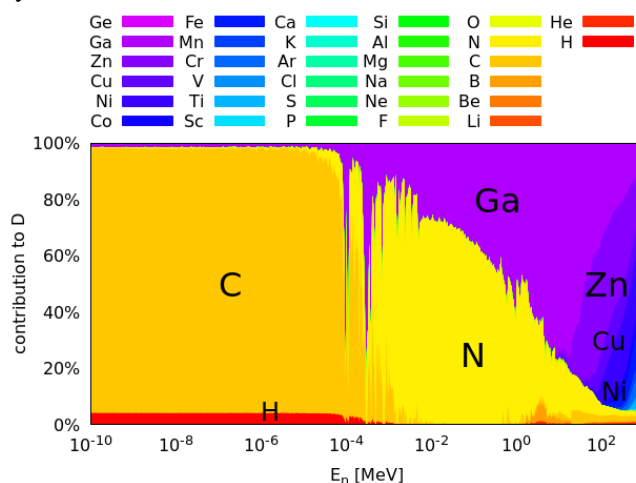


Fig. 11. PKA contributions to the n-GaN displacement damage cross-section (with TRIM energy partition function).

### V. CONSEQUENCES IN TEST PROCEDURES

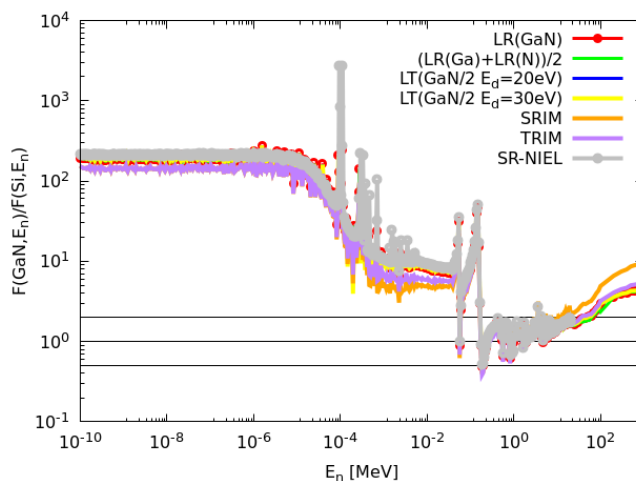


Fig. 12. Ratio of relative damage factor in GaN on relative damage in Si as a function of neutron energy.

As mentioned before, the tests are often performed using 1 MeV Silicon equivalent fluence. The ratio of relative damage factor in GaN on relative damage in Si as a function of neutron energy in Fig. 12 shows the error made if the Si curve is used instead of the GaN curve. The different modeling hypotheses give close results. We can observe that:

- between 10 MeV and 1 GeV, the error is between 2 and 10;
- between 0.1 MeV and 10 MeV, the error is less than

100%, which can be considered acceptable in many cases;

- between 100 eV and 100 keV, the error is about one order of magnitude ( $\sim 10$ );
- and below 10 eV, the error is of the order of two orders of magnitude.

In summary, the error is reasonable for values close to 1 MeV, strong for high energies and very strong for low energies. It confirms that this is something to carefully take into account, because depending on the particle energy spectrum, the error can change from negligible to very high.

TABLE I  
NIEL AND RATIO TO 1 MEV IN SI AND GaN FOR DIFFERENT NEUTRON SPECTRA (FORMULA IN APPENDIX)

NEUTRON SPECTRUM	NIEL IN SI	NIEL IN GaN
	AND RATIO TO 1 MEV	AND RATIO TO 1 MEV
1 MeV	2.0 keV.cm <sup>2</sup> /g(Si) [1.0]	0.47 keV.cm <sup>2</sup> /g(GaN) [1.0]
25 meV	48 eV.cm <sup>2</sup> /g(Si) [0.024]	75 eV.cm <sup>2</sup> /g(GaN) [0.16]
14 MeV	4.0 keV.cm <sup>2</sup> /g(Si) [2.0]	1.9 keV.cm <sup>2</sup> /g(GaN) [4.04]
Watt distribution	2.1 keV.cm <sup>2</sup> /g(Si) [1.05]	0.69 keV.cm <sup>2</sup> /g(GaN) [1.47]
Terrestrial spectrum	2.8 keV.cm <sup>2</sup> /g(Si) [1.4]	1.1 keV.cm <sup>2</sup> /g(GaN) [2.34]

If we know a neutron spectrum, we can estimate the neutron NIEL in Si and in GaN. Table I displays the NIEL and ratio to 1 MeV in Si and GaN for different classic neutron spectra. NIEL at 1 MeV is also chosen as the reference because it is commonly used for Si even if for GaN another energy could be chosen. For 25 meV, in Si, the ratio is very low ( $\sim 2.4\%$ ) and low in GaN ( $\sim 16\%$ ). For 14 MeV, in Si, the ratio is x2 and x4 in GaN. For a Watt distribution, the ratio is equal to  $\sim 1$  for Si and  $\sim 1.5$  for GaN. For the terrestrial spectrum, the ratio is about 1.4 in Si and 2.34 in GaN. For these spectra, the ratios at 1 MeV are very different between Si and GaN. Neither the energy-dependent shape of the NIEL silicon displacement damage curve nor its 1 MeV reference normalization value are directly applicable to represent displacement damage in GaN.

## VI. CONCLUSION

In this paper, we have presented and used a numerical method to evaluate the damage displacement damage cross section for GaN components under neutron irradiation in an energy range between 0.1 meV and 1 GeV.

After a quick presentation of the method models, we have chosen some of them for evaluations of the displacement damage cross section of the n-Si and n-GaN interactions. We have shown that using Si data for GaN components leads to underestimate the displacement levels. Between 0.1 MeV and 10 MeV, the error is less than 100%. Between 100 eV and 100 keV, the error is about one order of magnitude. Between 10 MeV and 1 GeV, the error is between two and ten. Below 10 eV, the error is around two orders of magnitude. For the characterization of displacement effects of GaN components, we strongly recommend to use the NIEL n-GaN values instead

of other values.

Furthermore, we have shown that, contrary to Si, the PKA distributions are different according to the energy ranges. The main PKA is the C ion at very low energy ( $< 10$  eV). Between  $\sim 1$  and 100 keV, it is the N ion, while it is Ga at medium energy and a mix of different heavy ions at high energy. As has been done previously for Si [23][46], this work will be used as a starting point for future exhaustive studies based on atomistic modeling, in order to understand the radiation hardness of GaN components to displacement damage. For example, a study of the temporal evolution of cascades induced by N or Ga ions could allow a better understanding of the link between the displacement dose level and the number of stable residual defects that affect the relevant displacement damage modes.

These numerical data will be useful to validate experimentally the relative damage factor and to determine if this classical approach, used for silicon devices, is also suitable for GaN devices. This is the first step of an ambitious numerical and experimental study. The final goal is to reach an experimentally validated standard like the one in [4]. The following step will be to link this numerical data to the response of GaN devices after neutron irradiation.

## APPENDIX

Watt distribution spectrum formula between 1 keV and 10 MeV:

$$\frac{d\phi(E)}{dE} = 0.4865 \sinh(\sqrt{2E})e^{-E}$$

Terrestrial neutron spectrum between 1 MeV and 1 GeV [48]:

$$\begin{aligned} \frac{d\phi(E)}{dE} = & 1.006 \times 10^{-6} \exp(-0.35(\ln(E)^2) + 2.1451\ln(E)) \\ & + 0,001011 \times 10^{-3} \exp(-0.4106(\ln(E)^2) \\ & - 0.667\ln(E)) \end{aligned}$$

## ACKNOWLEDGMENT

The authors thank Jean-Luc Leray and Thomas Jarrin for useful discussions on neutron spectra and displacement damage.

## REFERENCES

- [1] G. C. Messenger, "Displacement damage in silicon and germanium transistors," *IEEE Trans. Nucl. Sci.*, vol. 12, no. 2, pp. 53-74, April 1965, 10.1109/TNS.1965.4323568.
- [2] G. C. Messenger, "Radiation effects on microcircuits," *IEEE Trans. Nucl. Sci.*, vol. 13, no. 6, pp. 141-159, Dec. 1966, 10.1109/TNS.1996.4324356.
- [3] J.C. Boudenot and E. Daly "Short course 1: Radiative environment, interaction mechanisms, protection, and shielding, new models for space environment," presented at the 2<sup>nd</sup> European Conference *RADIATION Effects on Components and Systems*, Saint Malo, France, 1993
- [4] C. Inguibert and R. Gigante, "NEMO: a code to compute NIEL of protons, neutrons, electrons, and heavy ions," *IEEE Trans. Nucl. Sci.*, vol. 53, no. 4, pp. 1967-1972, Aug. 2006, 10.1109/TNS.2006.880926.
- [5] P. G. Rancoita *et al* "Screened relativistic (SR) treatment for NIEL dose nuclear and electronic stopping power calculator (Version 9.0)" [Online] Available: <http://www.sr-niel.org>, Accessed on Dec. 12, 2022
- [6] E722-19, Standard practice for characterizing neutron fluence spectra in terms of an equivalent monoenergetic neutron fluence for radiation-hardness testing of electronics, ASTM International, West Conshohocken, www.astm.org, 2019



- [7] B. D. Weaver, P. A. Martin, J. B. Boos and C. D. Cress, "Displacement damage effects in AlGaIn/GaN high electron mobility transistors," *IEEE Trans. Nucl. Sci.*, vol. 59, no. 6, pp. 3077-3080, Dec. 2012, 10.1109/TNS.2012.2224371.
- [8] J-M. Lauenstein "Short course wide bandgap power – SiC, GaN – Radiation reliability" presented at the *IEEE Nuclear and Space Radiation Effects Conference*, Santa Fe, New Mexico, USA, July 2020
- [9] C. Ngom *et al* "Backside laser testing of single-event effects in GaN-on Si power HEMTs," *IEEE Trans. Nucl. Sci.*, vol. 68, no. 8, pp. 1642-1650, Aug. 2021, 10.1109/TNS.2021.3081485.
- [10] D. Munteanu and J. L. Autran, "Terrestrial neutron-induced single events in GaN," *Microelect. Rel.*, vol. 100–101, no. 113357, Sept. 2019, 10.1016/j.microrel.2019.06.049
- [11] J. M. Osheroff, J. -M. Lauenstein and R. L. Ladbury, "LET and range characteristics of proton recoil ions in gallium nitride (GaN)," *IEEE Trans. Nucl. Sci.*, vol. 68, no. 5, pp. 597-602, May 2021, 10.1109/TNS.2021.3050980.
- [12] J. W. McClory and J. C. Petrosky, "Temperature dependent electrical characteristics of neutron irradiated AlGaIn/GaN HFETs," *IEEE Trans. Nucl. Sci.*, vol. 54, no. 6, pp. 1969-1974, Dec. 2007, 10.1109/TNS.2007.910852.
- [13] F. Berthet *et al.*, "Influence of neutron irradiation on electron traps existing in GaN-based transistors," *IEEE Trans. Nucl. Sci.*, vol. 63, no. 3, pp. 1918-1926, June 2016, 10.1109/TNS.2016.2566683.
- [14] P. A. Butler, M. J. Uren, B. Lambert and M. Kuball, "Neutron irradiation impact on AlGaIn/GaN HEMT switching transients," *IEEE Trans. Nucl. Sci.*, vol. 65, no. 12, pp. 2862-2869, Dec. 2018, 10.1109/TNS.2018.2880287.
- [15] L. Lv *et al.*, "Significant degradation of AlGaIn/GaN high-electron mobility transistors with fast and thermal neutron irradiation," *IEEE Trans. Nucl. Sci.*, vol. 66, no. 6, pp. 886-891, June 2019, 10.1109/TNS.2019.2899406.
- [16] J. Xu *et al.*, "Early stage degradation related to dislocation evolution in neutron irradiated AlGaIn/GaN HEMTs," *Appl. Phys. Lett.*, vol 117, no. 023501, July 2020, 10.1063/5.0011995
- [17] C. Poivey "TNID total non ionizing dose or DD displacement damage," presented at the *ESA – CERN – SCC Workshop*, CERN, May 9-10, 2017
- [18] E. E. Conrad, "Considerations in establishing a standard for neutron displacement energy effects in semiconductors," *IEEE Trans. Nucl. Sci.*, vol. 18, no. 6, pp. 200-205, Dec. 1971, 10.1109/TNS.1971.4326433.
- [19] A. I. Namenson, E. A. Wolicki and G. C. Messenger, "Average silicon neutron displacement kerma Factor at 1 MeV," *IEEE Trans. Nucl. Sci.*, vol. 29, no. 1, pp. 1018-1020, Feb. 1982, 10.1109/TNS.1982.4336006.
- [20] D. Lambert, O. Riant, D. Thouvenot, E. Feuilloley and T. Colladant, "Evaluation of the displacement damage equivalent fluence from different facilities and devices," in *18<sup>th</sup> European Conference on Radiation and Its Effects on Components and Systems (RADECS)*, Gothenburg, Sweden, 2018, pp. 72-78, 10.1109/RADECS45761.2018.9328661.
- [21] UMAS Lowell, "Neutron facilities," [Online]. Available: <https://www.uml.edu/Research/RadLab/Neutron-Facilities.aspx/>, Accessed on Dec. 12, 2022
- [22] TRIUMF, "Calculator of 1-MeV equivalent neutron fluences," [Online]. Available: <https://www.triumf.ca/pif-nif/calculator-1-mev-equiv>, Accessed on Dec. 12, 2022
- [23] M. Raine *et al.*, "Simulation of single particle displacement damage in silicon – part I: global approach and primary interaction simulation," *IEEE Trans. Nucl. Sci.*, vol. 64, no. 1, pp. 133-140, Jan. 2017, 10.1109/TNS.2016.2615133.
- [24] A. Vasilescu and G. Gunnar "Notes on the fluence normalisation based on the NIEL scaling hypothesis", Version Aug 15, 2000, [Online] Available: <https://rd50.web.cern.ch/rd50/NIEL/>, Accessed on Dec. 12, 2022
- [25] J. Allison *et al.*, "Geant4 developments and applications," *IEEE Trans. Nucl. Sci.*, vol. 53, no. 1, pp. 270-278, Feb. 2006, 10.1109/TNS.2006.869826.
- [26] S. Agostinelli *et al.*, "Geant4 - a simulation toolkit," *Nuc. Inst. and Met. in Phys. Res. Section A: Acc. Spect., Det. and Ass. Eq.*, vol. 506, no. 3, pp. 250-303, July 2003, 10.1016/S0168-9002(03)01368-8.
- [27] J. Allison *et al.*, "Recent developments in Geant4," *Nuc. Inst. and Met. in Phys. Res. Section A: Acc. Spect., Det. and Ass. Eq.*, vol. 835, pp. 186-225, Nov. 2016, 10.1016/j.nima.2016.06.125.
- [28] M. J. Norgett, M. T. Robinson and I. M. Torrens, "A proposed method of calculating displacement dose rates," *Nuc. Eng. and Des.*, vol. 33, no. 1, pp. 50-54, Aug. 1975, 10.1016/0029-5493(75)90035-7.
- [29] J. Lindhard, V. Nielsen, M. Scharff and P.V. Thomsen "Integral equations governing radiation effects (notes on atomic collisions, III)," *Mat. Fys. Medd. Dan. Vid. Selsk.*, vol. 33, no 10, pp. 1-42, 1963
- [30] J. Lindhard, M. Scharff and H. Schiott, "Range concepts and heavy ion ranges (notes on atomic collisions, III)," *Mat. Fys. Medd. Dan. Vid. Selsk.*, vol. 33, no 14, pp. 1-40, 1963.
- [31] I. Jun, "Effects of secondary particles on the total dose and the displacement damage in space proton environments," *IEEE Trans. Nucl. Sci.*, vol. 48, no. 1, pp. 162-175, Feb 2001, 10.1109/23.907581
- [32] G. H. Kinchin and R. S. Pease, "The displacement of atoms in solids by radiation," *Rep. on Prog. in Phys.*, vol. 18, pp. 1-51, 1955, 10.1088/0034-4885/18/1/301
- [33] K. Nordlund *et al* "Primary radiation damage in materials - review of current understanding and proposed new standard displacement damage model to incorporate in-cascade defect production efficiency and mixing effects," OECD/NEA, 2015. [Online]. Available [https://inis.iaea.org/collection/NCLCollectionStore/\\_Public/46/066/46066650.pdf](https://inis.iaea.org/collection/NCLCollectionStore/_Public/46/066/46066650.pdf) Accessed on: Feb. 13, 2023
- [34] C. Inguibert, "Including a distribution of threshold displacement damage energy on the calculation of the damage function and electron's Non Ionizing energy Loss," *Journal of Nuc. Mat.*, vol. 559, no 153398, Feb. 2022, 10.1016/j.jnucmat.2021.153398.
- [35] M. Huhtinen, "Simulation of non-ionising energy loss and defect formation in silicon," *Nuc. Inst. and Met. in Phys. Res. Section A: Acc. Spect., Det. and Ass. Eq.*, vol. 491, no 1–2, pp. 194-215, Sept. 2002, 10.1016/S0168-9002(02)01227-5.
- [36] J. Ziegler, "The stopping and range of ions in matter," SRIM-2013, 2013 [Online] Available <http://www.srim.org> Access on: Dec. 12, 2022
- [37] J. F. Ziegler, J. P. Biersack and M. D. Ziegler, "TRIM: scientific background," in SRIM The stopping and range of ions in matter, Chester, MD, USA, 2008, pp. 1-36, ISBN-13 978-0965420716
- [38] S. Agarwal, Y. Lin, C. Li, R.E. Stoller and S.J. Zinkle, "On the use of SRIM for calculating vacancy production: Quick calculation and full-cascade options," *Nuc. Inst. and Met. in Phys. Res. Section B: Beam Int. with Mat. and At.*, vol. 503, pp. 11-29, Sept. 2021, 10.1016/j.nimb.2021.06.018
- [39] S. Pearton *et al* "Review of radiation damage in GaN-based materials and devices," *Journal of Vac. Sc. and tech. A*, vol. A 31, Ap. 9 2013, 10.1116/1.4799504
- [40] K. Aoshima, M. Horita, and J. Suda "Correlation between non-ionizing energy loss and production rates of an electron trap formed by various types of radiation in gallium nitride," presented at the *European Conference on Radiation and Its Effects on Components and Systems (RADECS)*, Venice, Italia, Oct. 3-7 2022
- [41] M. Horita, T. Narita, T. Kachi, and J. Suda, "Nitrogen-displacement related electron traps in n-type GaN grown on a GaN freestanding substrate," *Appl. Phys. Lett.*, vol. 118, no. 012106, Jan., 2021, 10.1063/5.0035235.
- [42] J. Nord, K. Nordlund, J. Keinonen, and K. Able, "Molecular dynamics study of defect formation in GaN cascades," *Nuc. Inst. and Met. in Phys. Res. Section B: Beam Int. with Mat. and At.*, vol. 202, no. 93, Apr. 2003, 10.1103/PhysRevB.68.184104.
- [43] Nuclear Energy Agency "JANIS" Vers. 4.1 Sept 2020, [Online] Available: <https://www.oecd-nea.org/janisweb>, Accessed on Dec. 12, 2022
- [44] C. A. Coulter and D. Parkin "Damage energy functions in polyatomic materials," *Journal of Nuclear Materials* vol. 88, pp. 249-260, 1980
- [45] A. Coronetti, R. Garcia, D. Lucsanyi, M. Letiche, and F. Saigné "An analysis of the criticality of the  $^{14}\text{N}(n,p)^{14}\text{C}$  reaction for single-event upsets induced by thermal neutrons in SRAMs," presented at the *European Conference on Radiation and Its Effects on Components and Systems (RADECS)*, Venice, Italia, Oct. 3-7 2022
- [46] A. Jay *et al.*, "Simulation of Single Particle Displacement Damage in Silicon—Part II: Generation and Long-Time Relaxation of Damage Structure," *IEEE Trans. Nucl. Sci.*, vol. 64, no. 1, pp. 141-148, Jan. 2017, 10.1109/TNS.2016.2628089.
- [47] T. Jarrin, A. Jay, M. Raine, N. Mousseau, A. Hémerlyck and N. Richard, "Simulation of Single Particle Displacement Damage in  $\text{Si}_{1-x}\text{Ge}_x$  Alloys—Interaction of Primary Particles With the Material and Generation of the Damage Structure," *IEEE Trans. Nucl. Sci.*, vol. 67, no. 7, pp. 1273-1283, July 2020, 10.1109/TNS.2020.2970488.
- [48] JEDEC Solid State Technology Association, JEDEC Standard, Measurement and reporting of alpha particle and terrestrial cosmic ray-induced soft errors in semiconductor devices, JESD89A (Revision of JESD89, August 2001), October 2006